

# The Effect of Horn Beetle Nano Chitosan (*Xylotrupes gideon*) on the Surface Roughness of Glass- Ionomer Cement

*by Rosalina Tjandrawinata*

---

**Submission date:** 07-Apr-2023 02:34PM (UTC+0700)

**Submission ID:** 2058251975

**File name:** Materials\_Science\_Forum\_31\_Agustus\_2022.pdf (347.97K)

**Word count:** 2996

**Character count:** 15857

## The Effect of Horn Beetle Nano Chitosan (*Xylotrupes gideon*) on the Surface Roughness of Glass-Ionomer Cement

Florencia Livia<sup>1,a \*</sup>, Rosalina Tjandrawinata<sup>1,b</sup>,  
Carolina Damayanti Marpaung<sup>2,c</sup>, Deviyanti Pratiwi<sup>1,d</sup>  
and Komariah Komariah<sup>3,e</sup>

<sup>1</sup>Department of Dental Material Science and Technology, Faculty of Dentistry Universitas Trisakti, Campus B, Jl. Kyai Tapa 260, Grogol, Jakarta 11440, Indonesia

<sup>2</sup>Department of Orthodontics, Faculty of Dentistry Universitas Trisakti, Campus B, Jl. Kyai Tapa 260, Grogol, Jakarta 11440, Indonesia

<sup>3</sup>Department of Oral Biology, Faculty of Dentistry Universitas Trisakti, Campus B, Jl. Kyai Tapa 260, Grogol, Jakarta 11440, Indonesia

\*florencia@trisakti.ac.id, <sup>b</sup>rosalina@trisakti.ac.id, <sup>c</sup>carolina@trisakti.ac.id, <sup>d</sup>deviyanti@trisakti.ac.id, <sup>e</sup>komariah@trisakti.ac.id

**Keywords:** Glass ionomer cement, nano chitosan horn beetle, surface roughness

**Abstract.** The purpose of this study was to evaluate the effect of adding horn beetle nano chitosan (NCH) to Glass Ionomer Cement (GIC) liquid on surface roughness. The evaluation was done before and after the addition of NCH and from the length of time soaking in artificial saliva. The disc sample with a diameter of 6 mm and a height of 3 mm of total 40 samples were divided into four groups: the GIC control group, GIC modified NCH 0.5%, 1%, and 2%. Each sample was immersed for 24 hours and seven days in artificial saliva. Surface roughness before and after immersion was measured using the Surtronic S-100 Series Surface Roughness Tester. Data analysis was performed using a one-way ANOVA test to determine the effect of adding horn beetle NCH and paired *t*-test to determine the effect of immersion time on the surface roughness of GIC. Although the highest surface roughness values were found in sample GIC modified NCH 1% ( $2.51 \pm 0.86$  for 24 hours) and in sample GIC modified NCH 2% ( $2.64 \pm 0.84$  for 7 days), there was no significant differences for both the surface roughness with the addition of NCH ( $p > 0.05$ ) and the length of immersed time ( $p > 0.05$ ). As the conclusion, there is no effect of horn beetle nano chitosan to GIC surface roughness. However, the addition of horn beetle NCH presented rougher surfaces after immersion. These experiments can help predict the performance of these materials under clinical conditions.

### Introduction

Glass Ionomer Cement (GIC) is a tooth-colored restorative material used in dentistry. GIC is used widely because of its ability to release fluoride which prevents caries, biocompatible, and it has similar thermal expansion with tooth structure. On the other hand, GIC is also brittle because it has low acid resistance so it's easy to erode, dissolves, and cause surface roughness, high surface tension between components and weak adhesion between components so that the mechanical properties of GIC are relatively poor [1].

Surface roughness is an irregular surface characteristic of restorative materials and can be a retention of plaque accumulation to trigger caries. Glass Ionomer Cement is a restorative material that has a fairly high surface roughness value. In its development, the weakness of GIC filling material was improved by adding materials that could increase the GIC resistance. Materials added to improve the weaknesses of GIC are in the form of metals and resins [2]. Other materials developed to increase GIC resistance are chitosan natural materials [3].

Chitosan is a natural polymer which is very abundant in nature. Chitosan as a natural polymer has good characteristics, such as biodegradability, non-toxicity, adsorption, and antimicrobial properties because it can inhibit pathogenic bacteria and spoilage microorganisms including fungi, gram-

positive bacteria, and gram-negative bacteria. Chitosan can be made from insects and crustacean animal such as crab and shrimp. The advantage of chitosan natural ingredients compared to other materials is that chitosan is a natural material that is easily obtained, has economic value, and its activities can be applied in the fields of fisheries, agriculture, industrial environment, beauty, pharmacy, health, and food. Chitosan mixed in GIC manipulation can reduce GIC surface tension. This occurs when powder mixes with liquid GIC, chitosan's particle will be involved in increasing acid-base reactions with liquid GIC so that more salt bridges and cross-linking are formed. After reacting, the chitosan's particle will be adsorbed on the GIC matrix and fill between the glass particles. In addition, it can also increase GIC resistance to erosion due to acidic solutions, thereby reducing GIC surface roughness values [4].

Indonesia is a country known for its abundant marine products. As a food commodity that has economic value, so far, crustaceans are only used for their meat as a mixture for making crackers, shrimp paste or animal feed [5]. In addition to shrimp and crabs, insects can be also used as chitosan. Insect chitosan is derived from the head, skin or carapace. Insects are the largest group of animals, which is about 75% of the total number of living things. Some insects are beneficial but many are very harmful because they damage crops and spread disease to humans and livestock. One of the insects that is found widely in Indonesia (Bogor, Jawa Barat) and harms humans is horn beetle (*Xylotrupes gideon*) which mostly damages the shoots of coconut plants [5-6].

Chitosan modification has been done chemically and physically. Physical modification of chitosan is carried out to expand its utilization by changing the particle size of chitosan into nano chitosan. Chitosan nanoparticles can increase their ability to form bonds with other chemical substances. The development of chitosan into nano-forms can also improve the function of chitosan, one of which is inhibiting enamel demineralization [7].

Glass Ionomer Cement has a stable compressive strength at 24 hours of hardening. Based on previous research conducted by Nicholson, it was proven that the GIC experienced the most effective maturation process in compressive strength at a time duration of 7 days was  $199.4 \pm 12.0$  MPa. In addition, this study stated that the compressive strength value of GIC at 7 days was  $24.8 \pm 14.3$  MPa with the addition of acetic acid 45% in GIC [8]. Therefore, this study will be different from other research studies on modification of GIC with other chitosan, namely the manufacture of modified GIC samples of nano chitosan *Xylotrupes gideon* without the addition of acetic acid solvent.

## Materials and Methods

The research was conducted at the DMT CORE Laboratory, Faculty of Dentistry, Universitas Trisakti. Chitosan as raw material medicine formulations derived from demineralization, deproteinization, decolorization, deacetylation of exoskeletons *Xylotrupes gideon*, which has undergone physical modifications become nano chitosan [5]. Preliminary research was carried out in accordance with the methods listed. Preparation of GIC (GC Fuji Type IX, GC Corporation, Tokyo, Japan) without the addition of NCH and GIC with the addition of NCH were carried out. First, GIC was prepared without the addition of nano chitosan as a control group (GIC Control). Then the GIC group was made with the addition of chitosan where chitosan was added to the liquid GIC in three different concentrations, namely 0.5 wt% (GIC+NCH 0.5%); 1wt% (GIC+NCH 1%); 2wt% (GIC+NCH 2wt%) were mixed with GIC powder and manipulated manually according to the manufacturer's recommendations [9].

GIC is manipulated according to the manufacturer's instructions and put under pressure into a mold with a thickness and diameter that has been made according to the specification standard. The cement is put into the mold with a plastic spatula and compacted with the help of a cement stopper. After completely filling the mold, the celluloid strip was pressed onto it with the help of a 2 kg weight for 5 minutes. After completion, the sample dimensions were measured using a digital caliper. Then, the samples were immersed in artificial saliva for 24 hours and 7 days and put in an incubator at 37°C, then the dimensions were measured using a digital caliper.

The total number of samples were 40 samples which were made in pairs for 24 hours and 7 days immersed time. Each sample was made using mold with diameter of 6 mm and thickness of 3 mm, in

accordance with the ISO 9917-1:2007 standard. The surface roughness test was carried out on 40 samples which were divided into eight groups, namely the 24 hours immersion group consisting of GIC Control, GIC+NCH 0.5 wt%, GIC+NCH 1 wt%, GIC+NCH 2 wt% groups and the 7 days immersion group consisting of from GIC Control, GIC+NCH 0.5%, GIC+NCH 1%, GIC+NCH 2% groups. The samples were tested using a Surface Roughness Tester. Surface roughness testing was carried out using a Surface Roughness Tester (*Surtronic S-100 Series*) with the same measurement area in each test. Measurement of surface roughness was done by placing the sample on a glass plate and the sample was fixed using double-sided tape so that its position remains stable during measurement. Then the Surface Roughness Tester detector was placed on the specimen at an angle of 90° and the stylus was placed on the marked end of the specimen.

Analysis of the mean of each group was performed using SPSS software. The average value of each test group was subjected to one-way ANOVA statistical test. For data analysis based on the immersion time, a paired t-test would be carried out.

## Results

Fig. 1 showed there were no statistically significance differences of GIC control group and GIC modification nano chitosan group (one-way ANOVA,  $p > 0.05$ ) and no differences of 24 hours and 7 days immersed time (paired t-test,  $p > 0.05$ ). Normality test using the Kolmogorv-Smirnov test showed that the data of surface roughness test was 0.200 ( $p > 0.05$ ). The homogeneity test of surface roughness data was 0.152 ( $p > 0.05$ ). These results showed that the data of surface roughness test normally distributed and homogeneous.

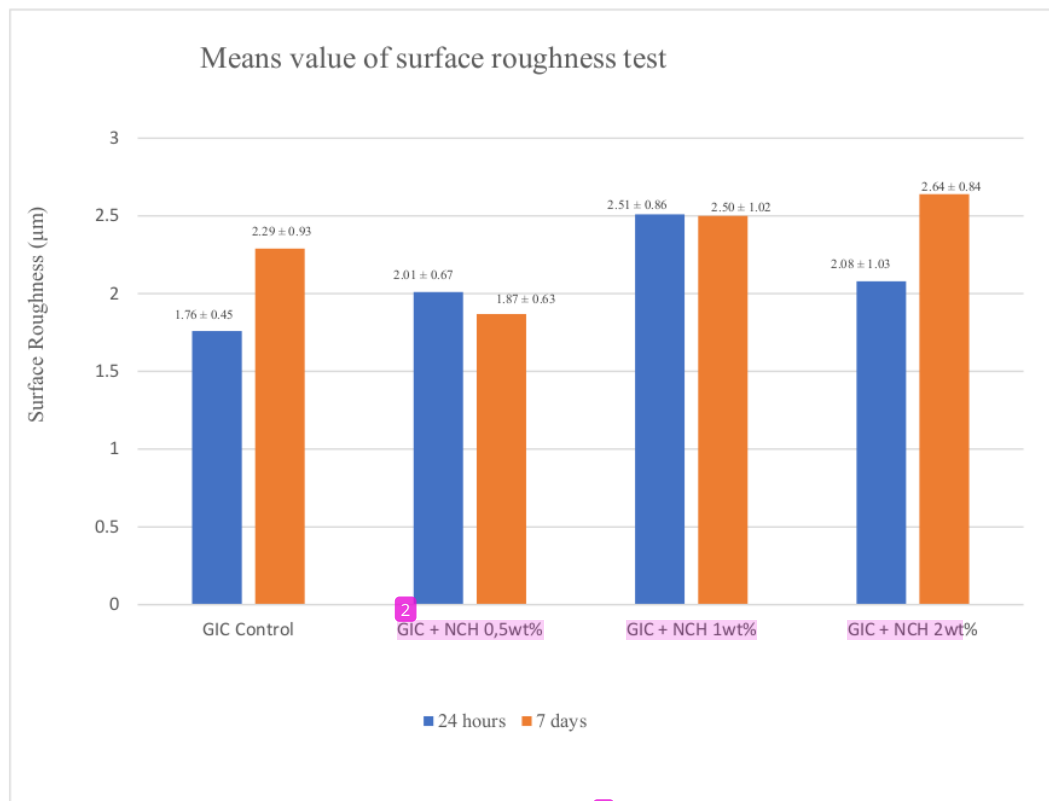


Figure 1. Surface roughness value of GIC Control, GIC+NCH 0.5 wt%, GIC+NCH 1 wt%, GIC+NCH 2 wt% with 24 hours and 7 days immersion time ( $p > 0.05$ ,  $n=10$ )

## Discussion

<sup>2</sup> Glass ionomer cement is a restorative material that is widely used by dentists because of its advantages such as minimal preparation, fluoride release, good flexural strength and biocompatible with tissues. Disadvantages of GIC are brittle and easily eroded, causing increase in surface roughness. Surface roughness in restorations can cause discoloration of fillings and accumulation of dental plaque which if left untreated can result in tooth decay and supporting tissue in the long term. In addition, the increase in surface roughness also causes susceptibility to microbial colonization which can increase the risk of occurrence of oral disease and indications of deterioration of restorative materials [10].

Glass ionomer cement is a restorative material that will experience changes in surface roughness in long-term use due to contamination from saliva and acid [9]. The surface roughness could make interaction with bacterial adhesion that still physico-chemically happen from certain distance by the attractive forces of van der Waal's bonding and also the forces of electrostatic repulsive [11]. Parameter value for measuring surface roughness used is the average diameter roughness (Ra). According to Bollen et al. [11], the critical surface roughness value for bacterial colonization of restorative materials is 0.2  $\mu\text{m}$ , if the surface roughness value is above 0.2  $\mu\text{m}$ , it has the potential to increase the attachment of bacteria and dental plaque which can increase the risk of caries. which can control the surface roughness of the restorative material such as the size, shape, and homogeneity of the particles [12]. The larger of the particle size of the materials, the higher results of surface roughness.

According to Bala O et al. [13], a small particle size will produce a lower surface roughness compared to a larger particle size. The small particles as in nano measurement give a better ability in improving physicochemical properties that already offers advantages in such various applications [5]. It was stated in the previous study from Soygun et.al [14] that CH-modified GIC was promising candidate for the future. This GIC modification study with horn beetle chitosan was not polished to determine the actual surface roughness value of the restorative materials. Therefore, it is possible that the surface roughness value was quite high both on immersion in artificial saliva for 24 hours and 7 days. There is no significant difference in the statistical analysis test ( $p > 0.05$ ).

Study conducted by Tjandrawinata R et al. [10] determined the GIC group that received the coating had a greater hardness value that was statistically significantly higher (t-test,  $p < 0.05$ ) than the GIC group with no coating. The hardness may be influence the surface roughness of GIC. To improve the physical properties of the GIC, polishing and the application of coating added to the restoration surface can be carried out. <sup>3</sup>

Soygun et al. [14] examined the addition of 5% and 10% CH to GIC liquid did not increase the surface roughness of GIC. In a study by Silva and Zuanon [15] which evaluated surface roughness values after hardening of four different traditional GICs used in Atraumatic Restorative Treatment (ART), it was reported that with the exception of the Vitro molar GIC group, all the other groups had roughness values below the clinically accepted Ra value determined by Bollen et al [11]. The mixture between CH and GIC could happen from hydroxyl and acetamide group of CH that form hydrogen bonds with powder's hydroxyl groups and polyacrylic acid's carboxylic acid group. The interfacial tension could be reduce and later it could improve the mechanical properties of GIC. The lowest Ra values of GIC could lead mixture to become homogenous from their chemical bonding [16]. Sharafeddin, et.al. stated that the CH solution is a water-soluble cationic polyelectrolyte since the amine groups are protonated and charged positively. It can also be called as strong base due to its amino group, which the  $\text{NH}_2$  group of CH and the functional group of the GIC (OH group and C = O group) could interact as their reaction mechanism. If CH concentration is increased then its molecules could react with each other instead of reacting with the GIC components [16].

### 3 Conclusion

In this in-vitro study, GIC modified nano chitosan was produced with the addition of nano chitosan horn beetle (*Xylotrupes gideon*) to Glass Ionomer Cement (GIC). The surface roughness results of GIC in artificial saliva of this study are presented that there were no statistically significance differences between control group and modification group. These materials under clinical conditions. A protective action against the carious process with significant surface damage due to erosion may be expected.

### References

- [1] F.A.P. Rizzante, R.S. Cunali, J.F.S. Bombonatti, G.M. Correr, C.C. Gonzaga, A.Y. Furuse. Indications and restorative techniques for glass ionomer cement. RSBO. 12 (2016) 79. DOI:10.21726/rsbo.v12i1.183
- [2] M. Almuhaiza. Glass-ionomer cements in restorative dentistry: A critical appraisal. J Contemp Dent Pract. 17 (2016) 331-336. DOI:10.5005/jp-journals-10024-1850
- [3] R.S. Kumar, N. Ravikumar, S. Kavitha, S. Mahalaxmi, R. Jayasree, T.S. Kumar, et al. Nanochitosan modified glass ionomer cement with enhanced mechanical properties and fluoride release. Ijbiomac. 104 (2017) 1860-1865.
- [4] K.J. Anusavice, R.W. Phillips, C. Shen, H.R. Rawls. Phillips 'Science of Dental Materials'. 12<sup>th</sup> ed. St.Louis, Mo.: Elsevier/Saunders. 2013;2012.
- [5] A. Komariah, R.A. Tatara, D.A. Bustami. Efficacy of Rhinoceros Beetle (*Xylotrupes Gideon*) Nano Chitosan and Calcium Mouthwash in Reducing Quantity Oral Cavity Bacteria among Elementary School Age Children. IJABBR. 5 (2017) 41-47.
- [6] G. Davis. The coconut Rhinoceros Beetle (*Oryctes rhinoceros*) with articular reference to the palau islands. Bernice P. Bishop Museum, Buletin. 212 (2001) 267-304.
- [7] R.C.F. Cheung, T.B. Ng, J.H. Wong, W.Y. Chan, Chitosan: An update on potential biomedical and pharmaceutical applications. Mar., Drugs. 13 (2015) 5156-5186.
- [8] S. Sidhu, J. Nicholson. A Review of Glass-Ionomer Cements for Clinical Dentistry. J Funct Biomater. 7 (2016) 16. doi:10.3390/jfb7030016
- [9] G.J. Mount. An Atlas of Glass-Ionomer Cement: A Clinician's Guide, third ed. Medicine & Health Science Books. 2001.
- [10] R. Tjandrawinata, M.W. Handoko, Octarina. The Effect of Nanofilled Resin Coating on the Hardness of Glass Ionomer Cement. Sci Dent J. 4 (2020) 97-100.
- [11] C.M.L. Bollen, P. Lambrechts, M. Quirynen. Comparison of surface roughness of oral hard materials to the threshold surface roughness for bacterial plaque retention: A review of the literature. Dent Mater. 13 (1997) 258-269.
- [12] R.S. Sayed, H.A. Shalaby, Y.F. Hussein Ali, N.K. Soliman. Surface Durability of Newly Glass Ionomer Cement Modified with Chitosan. IEEE Commun Surv Tutorials. 15 (2018) 75-83.
- [13] O. Bala, H.D. Arisu, I. Yikilgan, S. Arslan, A. Gullu. Evaluation of surface roughness and hardness of different glass ionomer cements. Eur J Dent. 6 (2012) 79-86.

- [14] K. Soygun, A. Soygun, M.C. Dogan. The effects of chitosan addition to glass ionomer cement on microhardness and surface roughness. *JABFM*. 19 (2021) 1–10. DOI: 10.1177/2280800021989706journals.sagepub.com/home/jbf
- [15] R.C.D. Silva, A.C.C. Zuanon. Surface roughness of glass ionomer cements indicated for atraumatic restorative treatment (ART). *Braz Dent J*. 17 (2006) 106-109.
- [16] F. Sharafeddin, Z. Jowkar, S. Bahrani, Comparison between the effect of adding microhydroxyapatite and chitosan on surface roughness and microhardness of resin modified and conventional glass ionomer cements, *J. Clin. Exp. Dent*. 13 8 (2021) e737–e744.

# Materials Science Forum 31 Agustus 2022

---

## ORIGINALITY REPORT

---

24%

SIMILARITY INDEX

21%

INTERNET SOURCES

13%

PUBLICATIONS

2%

STUDENT PAPERS

---

## PRIMARY SOURCES

---

1

[www.scientific.net](http://www.scientific.net)

Internet Source

10%

2

[jurnal.pdgi.or.id](http://jurnal.pdgi.or.id)

Internet Source

4%

3

Koray Soygun, Arzu Soygun, Muharrem Cem Dogan. "The effects of chitosan addition to glass ionomer cement on microhardness and surface roughness", Journal of Applied Biomaterials & Functional Materials, 2021

Publication

4%

4

[www.researchgate.net](http://www.researchgate.net)

Internet Source

3%

5

Rosalina Tjandrawinata, Brigitta Heidy, Octarina. "Effects of Red Dragon Fruit on Color Stability of Self-Adhesive Flowable Composite", Applied Mechanics and Materials, 2022

Publication

2%

6

[www.ncbi.nlm.nih.gov](http://www.ncbi.nlm.nih.gov)

Internet Source

2%

---

---

Exclude quotes      On

Exclude matches      < 2%

Exclude bibliography      On

mail.google.com/mail/u/0/#search/materials+science+forum+publication/FMfcgzGqQJhCTSTVTGqPQKQcndvcWPMQ

materials science forum publication

Active

Trans Tech Publications <authors@scientific.net>  
to me

Sat, Aug 27, 2022, 1:24 AM

**Scientific.Net**  
Publisher in Materials Science & Engineering

**Materials Science & Engineering**  
Online periodicals

Paper: «The Effect of Horn Beetle Nano Chitosan (*Xylotrupes gideon*) on the Surface Roughness of Glass-Ionomer Cement»

Journal: «**Materials Science Forum**»

Dear **Komariah Komariah**,

We are very pleased to announce that in less than 1 month, your paper «The Effect of Horn Beetle Nano Chitosan (*Xylotrupes gideon*) on the Surface Roughness of Glass-Ionomer Cement» will be published online in Journal «**Materials Science Forum Vol. 1069**».

In your [scientific.net](https://scientific.net) account, you can view the PDF version for your personal use only.

mail.google.com/mail/u/0/#search/materials+science+forum+publication/FMfcgzGqQJhCTSTVTGqPQKQcndvcWPMQ

materials science forum publication

Active

Your login credentials are:  
Login: [komariah@trisakti.ac.id](mailto:komariah@trisakti.ac.id)  
Password: WLMLP337  
Please, go to the upper left corner and choose 'Published Papers'.

In your author account, you will find information about additional opportunities such as OPEN ACCESS and OFFPRINTS.

In case your organization agreed to a special OA price with Trans Tech Publications (TTP), you will get this special price in your author account. Otherwise, you will find journal regular APC for OA **publication** that TTP applies.

We hope you enjoyed working with us. For us, it has been a pleasure to collaborate with you, and we trust to be in touch soon for further **publication** opportunities with Scientific.net!

Please contact us for questions and further information at [authors@scientific.net](mailto:authors@scientific.net).

Best regards,  
The Publishing Team, Scientific.net

P.S. Ready to publish? Follow this [link](#) to submit your request.

Our publishing process assures

mail.google.com/mail/u/0/#search/materials+science+forum+publication/FMfcgzGqJhCTSTVTGqPQKQcmdvcWPMQ

materials science forum publication

Active

4 of 10

We hope you enjoyed working with us. For us, it has been a pleasure to collaborate with you, and we trust to be in touch soon for further **publication** opportunities with Scientific.net!

Please contact us for questions and further information at [authors@scientific.net](mailto:authors@scientific.net).

Best regards,  
The Publishing Team, Scientific.net

P.S. Ready to publish? Follow this [link](#) to submit your request.

Our publishing process assures

- A peer-review system, safeguarding COPE publishing ethics
- An author-friendly tool
- International Indexing

Please click [here](#) to read practical information about your Author Account.

Please write to [authors@scientific.net](mailto:authors@scientific.net) in case you have lost your login details to enter your account at [scientific.net](http://scientific.net).

9:25 AM 5/4/2024

mail.google.com/mail/u/0/#search/materials+science+forum+publication/FMfcgzGqJhCTSTVTGqPQKQcmdvcWPMQ

materials science forum publication

Active

4 of 10

- A peer-review system, safeguarding COPE publishing ethics
- An author-friendly tool
- International Indexing

Please click [here](#) to read practical information about your Author Account.

Please write to [authors@scientific.net](mailto:authors@scientific.net) in case you have lost your login details to enter your account at [scientific.net](http://scientific.net).

---

**Trans Tech Publications Inc.**  
Seestrasse 24c, CH-8806 Baech,  
Switzerland  
Tel: 41 (44) 922 10 22  
E-Mail: [office@scientific.net](mailto:office@scientific.net)

© 2022 Scientific.Net. All rights reserved

9:26 AM 5/4/2024

mail.google.com/mail/u/0/#search/materials+science+forum+publication/FMfcgzGqQJmnhrrBxhlxSdpnnTqJrgbd

materials science forum publication

Active

Trans Tech Publications <authors@scientific.net>  
to me

Wed, Aug 31, 2022, 4:07 PM

**Scientific.Net**  
Publisher in Materials Science & Engineering

**Materials Science & Engineering**  
Online periodicals

Paper: «The Effect of Horn Beetle Nano Chitosan (*Xylotrupes gideon*) on the Surface Roughness of Glass-Ionomer Cement»  
Journal: «Materials Science Forum»  
Book: «Materials and Biotechnologies»

Dear Komariah Komariah,

We would like to thank you for your efforts to help produce this new journal volume, which contains your paper «The Effect of Horn Beetle Nano Chitosan (*Xylotrupes gideon*) on the Surface Roughness of Glass-Ionomer Cement» and can now be found online. The Journal volume will also appear as a book with an ISBN:

[Materials Science Forum Vol. 1069](#)

mail.google.com/mail/u/0/#search/materials+science+forum+publication/FMfcgzGqQJmnhrrBxhlxSdpnnTqJrgbd

materials science forum publication

Active

Dear Komariah Komariah,

We would like to thank you for your efforts to help produce this new journal volume, which contains your paper «The Effect of Horn Beetle Nano Chitosan (*Xylotrupes gideon*) on the Surface Roughness of Glass-Ionomer Cement» and can now be found online. The Journal volume will also appear as a book with an ISBN:

[Materials Science Forum Vol. 1069](#)  
[Materials and Biotechnologies](#)

We would appreciate it if you share this mail with your colleagues who might be interested in this field of research and or with your information manager or librarian.

Your login credentials are:  
Login: [komariah@trisakti.ac.id](mailto:komariah@trisakti.ac.id)  
Password: WLMLP337  
Please, go to the upper left corner and choose 'Published Papers'.

Thank you very much for your collaboration, time, and support.

Kind regards,  
Scientific.net Publishing Team

**PS:** Last but not least we are pleased to let you know that

mail.google.com/mail/u/0/#search/materials+science+forum+publication/FMfcgzGqQJmnhrrBxhlxSdpnnTqJrgbd

materials science forum publication

Active

3 of 10

Scientific.Net Publishing Team

**PS:** Last but not least we are pleased to let you know that

- We offer you a special discount for the print or e-Book that contains your paper(s).
- We would like to bring to your attention our [Specialized Collections](#) series presenting the carefully selected papers on the niche topics of **materials science** and engineering. We believe that it will be of great use for practical engineers, scientific researchers and broader academic groups and thus are happy to offer you a 25% discount on any book from this series by the following promocode **ADD20SCMAIL21**.  
The most recent book of this collection - [Sustainable Architecture](#) - is already available!
- Ready to publish? Follow this [link](#) to submit your request.

Our publishing process assures

- A peer-review system, safeguarding COPE publishing ethics
- An author-friendly tool
- International Indexing

Please click [here](#) to read practical information about your Author Account.

Please write to [authors@scientific.net](mailto:authors@scientific.net) in case you have lost your login details to enter your account at [scientific.net](http://scientific.net).

9:24 AM 5/4/2024

mail.google.com/mail/u/0/#search/materials+science+forum+publication/FMfcgzGqQJmnhrrBxhlxSdpnnTqJrgbd

materials science forum publication

Active

3 of 10

The most recent book of this collection - [Sustainable Architecture](#) - is already available!

- Ready to publish? Follow this [link](#) to submit your request.

Our publishing process assures

- A peer-review system, safeguarding COPE publishing ethics
- An author-friendly tool
- International Indexing

Please click [here](#) to read practical information about your Author Account.

Please write to [authors@scientific.net](mailto:authors@scientific.net) in case you have lost your login details to enter your account at [scientific.net](http://scientific.net).

---

**Trans Tech Publications Inc.**  
Seestrasse 24c, CH-8806 Baech,  
Switzerland  
Tel: 41 (44) 922 10 22  
E-Mail: [office@scientific.net](mailto:office@scientific.net)

9:25 AM 5/4/2024